

The Effect of the delignification of wood fibers on the mechanical properties of kraft pulp/polypropylene composites

Majid Kiaei^{1,*}, Ramin Vaysi¹, Behzad Kord²

1. Department of Wood and Paper Science and Technology, Islamic Azad University (IAU), Chaloos Branch, Iran;
2. Assistant Professor, Department of Paper and Packaging Technology, Faculty of Chemistry and Petrochemical Engineering, Standard Research Institute (SRI), Karaj, P. O. Box 31745-139, Iran;

*Corresponding author email: mjd_kia59@yahoo.com

ABSTRACT: In this study, the effects of alkalinity and cooking time (residual lignin content) on the mechanical strength of Kraft pulp/polypropylene composites were studied. For this purpose, hornbeam wood chips were converted to Kraft pulp at three different alkalinities (15, 20, and 25%) and three different cooking times (60, 90, and 120 min). The residual lignin contents of these pulps were determined according to the TAPPI standard. Kraft pulp was mixed with polypropylene (PP) at 50% weight ratios. The amount of maleic anhydride (MAPP) coupling agent was fixed at 4 per hundred compounds (phc) for all formulations. The results indicated that the tensile strength, tensile modulus, flexural strength, and flexural modulus were increased by increasing the alkalinity and cooking time; however, the notched impact strength decreased.

Keywords: Alkalinity; Cooking time; Residual lignin content; Mechanical properties;

INTRODUCTION

Lignin is widely distributed throughout the cell walls of wood, but it is highly deposited in the middle lamella region and its typically present at 20-30% in wood (Woodhams *et al.* 1984). Lignin is a branched heterogeneous aromatic polymer formed of phenylpropane units linked together primarily by β -O-4 arylether linkages (50 to 60% of all linkages). Lignin is characterized by the presence of different functional groups, such as phenolics, methoxyls, aliphatic alcohols, aldehydes, ketones, and ethers (Zakis 1994). Sinapyl alcohol, coniferyl alcohol, and p-coumaryl alcohol are involved in the biosynthesis of hardwood lignin (Bonawitz 2010). In wood, there is a chemical connection between lignin and hemicelluloses. Because the lignin structure is both polar and nonpolar, lignin can cause more compatibility between polymer and wood flour in WPC materials. Lignocellulosic materials are polar by nature, whereas polymers are nonpolar by nature. Thus, a good connection between these two phases does not accrue in normal conditions (Behrooz *et al.* 2010).

Lignin is one of the major components of all natural fibers has poor reinforcing effects in composites when used alone. The removal of lignin from cellulosic fibers could help to improve the mechanical properties of natural fiber-plastic composites in two ways: by increasing the stronger and stiffer cellulose content at a given fiber fraction, and by improving the adhesion between the two phases of the composites through the elimination of the less chemically reactive lignin component (Karimi *et al.* 2006). Rozman *et al.* (2000) prepared acid lignin base using the Klason method as a coupling agent in coconut fiber-polypropylene composites. The results showed that the composite materials had better physical and mechanical properties than the control samples. Karimi *et al.* (2006) reported that delignified fibers improvement the tensile strength and tensile modulus, whereas the hardness of composites was unaffected by delignification. Delignified fibers also exhibited better water absorption resistance. Notched impact strength was higher for delignified fiber composites, but it was reduced at higher delignification levels. Beg and Pickering (2007) reported that residual lignin content decreased with progressive washing and bleaching. Fiber with higher amounts of residual lignin content led to composites with lower tensile and impact strengths and increased degradability when subjected to accelerated weathering testing.

The aim of this study was to investigate the influence of pulping condition variables such as the alkalinity and cooking time on the physical and mechanical properties of Kraft pulp/polypropylene composites.

MATERIALS AND METHODS

Materials

Several discs from hornbeam (*Carpinus betulus*) logs were obtained from the Sari region (Mazandaran Province, Iran) and then converted into chips. The chips were 20 mm in length and 4 mm thick, on average. The Kraft pulp of hornbeam wood was used as a filler material. The polymer matrix used in this study, PP, was supplied by Arak petrochemical industries (Arak, Iran) and had a melt flow index of 8 g/10 min and a density of 0.92 g/cm³. Composite profiles consisted of PP and Kraft pulp at 50% weight ratios. Polypropylene grafted with maleic anhydride (MAPP) with a melt flow index of 64 g/10 min as the coupling agent was acquired from Solvay Company, Belgium. The amount of coupling agent was fixed at 4 per hundred compounds (phc) for all formulations. The chemical materials used for cooking liquor include of Na₂S and NaOH were supplied by Merck Co. (Frankfurt, Germany).

METHODS

Kraft pulping

Having prepared wood chips of certain dimensions, the moisture content of the samples was determined. The variable factors were alkalinity (15, 20, and 25%) and cooking time (60, 90, and 120 min), while the constant factors were cooking temperature (170 °C), sulfidity (25%), Pressure 7 bar and the ratio of cooking liquor to dry weight of samples (7 to 1). At the end of the pulping process, the complete dry weight of the pulp sample was calculated after rinsing, drying, and calculating the moisture content. The Kappa number of the pulp was found based on the T236 om-99 standard. The results of cooking tests on the Kraft process demonstrated that three treatments, namely (a) 15% alkalinity and 60-min cooking time; (b) 15% alkalinity and 90-min cooking time; and (c) 15% alkalinity and 120-min cooking time, were not and strong enough. Therefore, these treatments were not sufficient to transform the wood chips into Kraft pulp. Thus, the T222 om-02 standard was used to determine the lignin content of these three treatments. The fibers obtained from alkalinities of 15, 20, and 25% were converted to flour at different times using a ball mill. The results of experiments on the Kraft pulp (Fig. 1) showed that by increasing the cooking time and the alkalinity, the Kappa number value was decreased. This can be attributed to the greater concentration of chemicals and thus higher rate of lignin-removal reactions. Meanwhile, the same trend was seen for the cooking time and may be due to the increased delignification at longer cooking times (Vaziri *et al.* 2009).

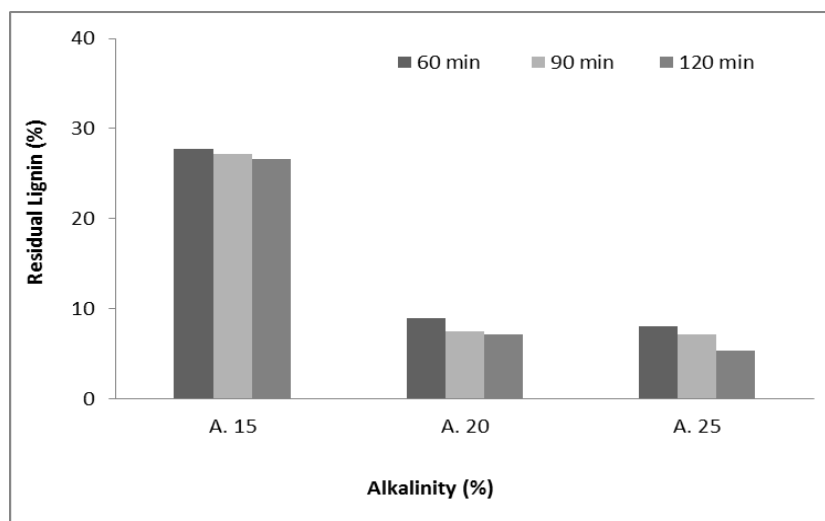


Figure 1. The effects of alkalinity and cooking time on the residual lignin in Kraft pulp

Processing of the composites

Before sample preparation, the Kraft pulp was dried in an oven at 70 ± 2 °C until it reached a constant weight. The mass ratio of Kraft pulp to polypropylene (PP) was controlled at 50:50% by weight for all blends. The amount of coupling agent was fixed at 4 per hundred compounds (phc) for all formulations. The mixing was carried out with a co-rotating twin-screw extruder (Model T20, 1990, Dr.Collin GmbH, Germany), with its barrel

temperature ranging from 140 to 160 °C at six zones, from feeding zone to the die zone, at a screw speed of 110 rpm. First, the polypropylene was fed to the mixing chamber, and after 2 minutes the PP was melted. Then, the coupling agent was added, the melting process of MAPP took in 3 minutes. At the fifth minute, the Kraft pulp was fed into the chamber, and the total mixing time was 13 min. The compounded materials were then ground using a pilot-scale grinder (WIESER, WGLS 200/200 Model). The resulting granules were dried at 105 °C for 4 h. Test specimens were injection molded according to ASTM D3641 standard by an injection molder at a molding temperature of 185 °C and injection pressure of 3 MPa (Eman machine, Aslanian Co, Iran). Finally, specimens were conditioned at a temperature of 23 °C and relative humidity of 50% for at least 40 h prior to testing according to ASTM D 618.

Mechanical properties

The flexural and tensile tests were conducted according to ASTM D 790 and D 638, respectively, using an Instron machine (Model 1186, England); the tests were performed at crosshead speeds of 5 mm/min. A Zwick impact tester (Model 5102, Germany) was used for the Izod impact test. All samples were notched at the center of one longitudinal side according to ASTM D 256.

Statistical analysis

The statistical analysis was conducted using Statistical Package for Social Science (SPSS, Version 16) in terms of one-way analysis of variance (ANOVA). The average values were compared and classified using the Duncan test at a 95% confidence level.

RESULTS AND DISCUSSION

Mechanical properties

Results of analysis of variance (ANOVA) indicated that the alkalinity, cooking time, and their interaction effects had a significant influence on the flexural strength, tensile strength, flexural modulus, tensile modulus, and impact strength of Kraft pulp/polypropylene composites (Table 1).

Table 1. F-value (in analysis of variance) of the results of kraft pulp/polypropylene composites

| Treatments | alkalinity (A) | cooking time (B) | A xB |
|-------------------|----------------|------------------|-----------|
| Flexural strength | 1346.775 ** | 144.125 ** | 19.989 ** |
| Flexural modulus | 1550.014 ** | 183.951 ** | 3.670 * |
| Tensile strength | 673.432 ** | 87.635 ** | 5.362 ** |
| Tensile modulus | 559.877 ** | 65.427 ** | 3.261 * |
| Impact strength | 1187.814 ** | 226.185 ** | 26.270 ** |

** and * were significant at 0.01 and 0.05

Impact Strength

Table 2 shows the effect of alkalinity and cooking time on the impact strength of Kraft pulp/polypropylene composites. This property decreased with increasing alkalinity and cooking time. The highest impact strength was observed for 15% alkalinity and 60-min cooking time; whereas the lowest impact strength corresponded to 25% alkalinity and 120-min cooking time. However, notched impact strength decreased with increasing alkalinity and cooking time. Izod impact energy is the energy required for crack propagation. The size and dispersion of filler particles in the matrix can affect the properties of the composites. Small well-dispersed particles generally lead to better properties. Small particles can block crack propagation and result in impact toughening. Particles with higher aspect ratios have high stresses at the fiber ends that can cause failure under impact (Beg and Pickering 2007).

Flexural and Tensile strength

The influence of alkalinity and cooking time on the flexural strength, flexural modulus, tensile strength, and tensile modulus of Kraft pulp/polypropylene composites is shown in Table 2. The tensile and flexural properties increased with increasing alkalinity and cooking time. The highest flexural and tensile strengths were observed for 25% alkalinity and 120-min cooking time, whereas the lowest mechanical strength corresponded to 15% alkalinity and 60-min cooking time. An increase in mechanical strength meant that the stress was successfully transferred from the PP matrix to the fibers. Delignified fibers transferred the stress better than the original fibers. This phenomenon resulted in a higher flexural and tensile strength due to the improvement of the adhesion and the nature of the fiber/matrix interface. It was expected that cellulose would have a better chemical reaction with the coupling agent compared with lignin due to a higher concentration of hydroxyl groups. Therefore, the elimination of

lignin from the fibers by higher alkalinity and cooking time improved interfacial bonding, which resulted in improvements in mechanical strength (Karimi *et al.* 2006; Beg and Pickering 2007).

Table 2. The effects of alkalinity and cooking time on mechanical properties of composites

| Cooking time | Alkalinity (%) | Flexural strength (MPa) | Flexural module (GPa) | Tensile strength (MPa) | Tensile module (GPa) | Impact strength (J/m) |
|--------------|----------------|-------------------------|-----------------------|------------------------|----------------------|-----------------------|
| 60 | 15 | 23.67 | 2.56 | 35.27 | 4.35 | 31.57 |
| | 20 | 26.21 | 2.83 | 41.57 | 4.72 | 25.32 |
| | 25 | 28.61 | 3.12 | 44.14 | 5.03 | 21.38 |
| 90 | 15 | 24.61 | 2.66 | 36.62 | 4.41 | 27.42 |
| | 20 | 26.90 | 2.88 | 42.25 | 4.83 | 23.82 |
| | 25 | 30.17 | 3.26 | 45.43 | 5.28 | 20.45 |
| 120 | 15 | 25.38 | 2.77 | 39.26 | 4.58 | 25.60 |
| | 20 | 27.73 | 2.99 | 43.18 | 4.94 | 22.83 |
| | 25 | 32.39 | 3.35 | 48.04 | 5.38 | 19.42 |

CONCLUSION

Increasing the alkalinity from 15 to 25% (decreasing residual lignin content) increased the values of modulus of elasticity, modulus of rupture, tensile strength, and tensile modulus by 21.7, 19.6, 23.6, and 6.17%, respectively; the notched impact strength decreased by 27.5%. Increasing the cooking time from 60 to 120 min (decreasing residual lignin content) increased the values of modulus of elasticity, modulus of rupture, tensile strength, and tensile modulus by 7, 8.8, 7.7, and 5.6%, respectively; and the notched impact strength decreased by 13.3%.

ACKNOWLEDGEMENTS

This research was funded by the Wood and Paper Science and Technology Chalous Branch, Islamic Azad University Chalous, Iran, in the form of a research plan. The authors appreciate the support received from the Islamic Azad University Chalous Branch, Iran.

REFERENCES

- Beg MD, Pickering KL. 2007. The effects of residual lignin content on wood fibre reinforced polypropylene composites. *Advance Materials Research* 29-30: 323-326.
- Behrooz R, Kordkheili HY, Najafi SK. 2010. Effect of lignin method on physical and mechanical properties of wood flour-polypropylene composites. *Iranian Journal of Wood and Paper Industries* 1(2): 103-113.
- Behrooz R, Kordkheili HY, Jalilvand M. 2009. Using wastes of OCC paper recycling mills. *Proceedings of 11th International Conference on Environmental Science and Technology, Greece, 3-5 September.*
- Bonawitz ND. 2010. The genetics of lignin biosynthesis: Connecting genotype to phenotype. *Annual Review of Genetics* 44(1): 337-363.
- Chanda M, Roy SK. 1998. *Plastics Technology Handbook*. 3rd Ed., Marcel Dekker, New York.
- Karimi A, Nazari S, Ghasemi I, Tajvidi M, Ebrahimi G. 2006. Effect of the delignification of wood fibers on the mechanical properties of wood fiber-polypropylene composites. *Journal of Applied Polymer Science* 102(5): 4759-4763.
- Rozman HD, Tan KW, Kumar RN, Abubakar A, Ishak M, Ismail H. 2000. The effect of lignin as a compatibilizer on the physical properties of coconut fiber polypropylene composites. *European Polymer Journal* 36(7): 1483-1494.
- Vaziri V, Hosseini SZ, Dehghani MR. 2009. Effect of altitude on fiber characteristics, chemical composition and kraft yield pulp of Brutian pine (*Pinus brutia*). *Journal of Wood and Forest Science and Technology* 16(1): 1-13.
- Woodhams RT, Thomas G, Rodgers DK. 1984. Wood fibers as reinforcing fillers for polyolefins. *Journal of Polymer Engineering Science* 24(15), 1166-1171.
- Zakis GF. 1994. *Functional Analysis of Lignins and Their Derivatives*, TAPPI Press, Atlanta, GA.